


## NOWOFOLON ET 6235 Z Film – White Standard S042.9/70 (250µm)


### Optical and Solar Properties

	Testmethod	Unit	Reference	2000 h
Light Reflexion Grade	Rvis	%	63,1	62,6
Solar Reflexion Grade	Rsol	%	48,7	48,6
Light Transmission Grade	Tvis	%	33,1	33,7
Solar Transmission Grade	Tsol	%	40,2	41,7
UV-Transmission Grade	Tuv	%	0,8	0,1
Shading Coefficient	SC	-	0,54	0,55
Solar Heat Gain Coefficient	SHGC	-	0,43	0,44
Colour Rendering Index	CRI	-	92,9	93,3

### Transmission / Reflection

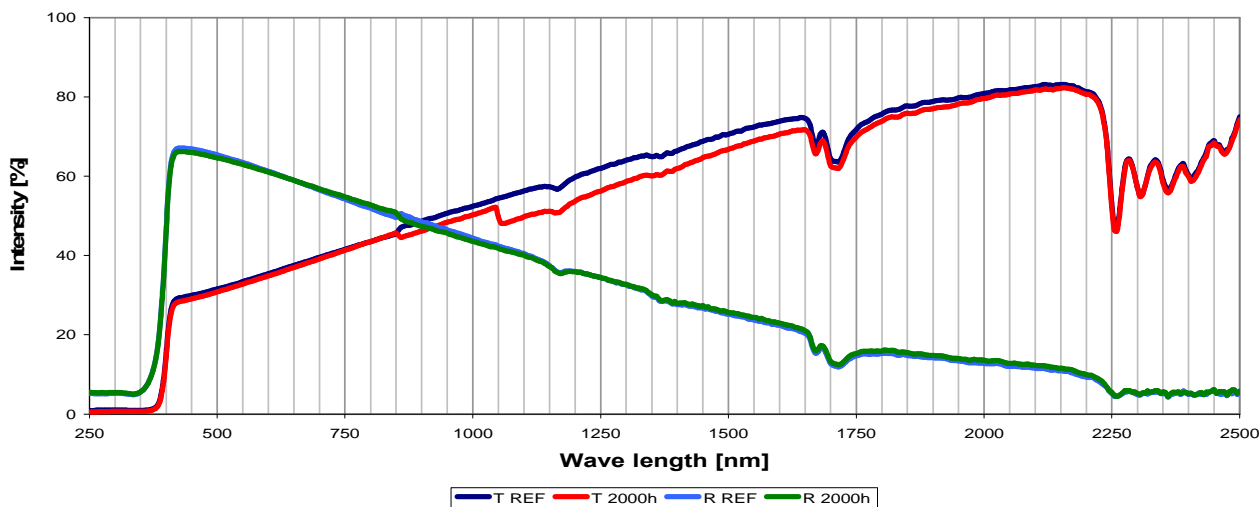

### Weatherability according to ISO 4892/2 Hunterlab – Lab-Standard

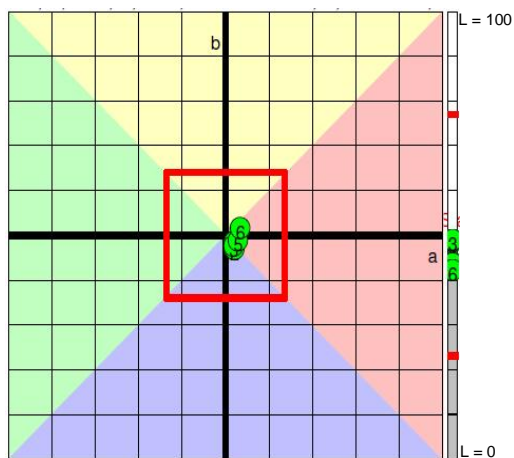

	Reference	2000h
L	93,86	92,30
a	-0,29	-0,12
b	2,66	2,74
Opacity (%)	70,7	71,1

#### Evaluation:

- Stable
- Conditionally Stable
- Visible Discolouring
- Discolouring
- Unstable